


**SPECIAL ALLOYS™**

**TOTAL WELDING**  
**SOLUTIONS FOR THE LNG INDUSTRY**

[www.lincolnelectric.eu](http://www.lincolnelectric.eu)

**LINCOLN®**  
**ELECTRIC**  
THE WELDING EXPERTS®

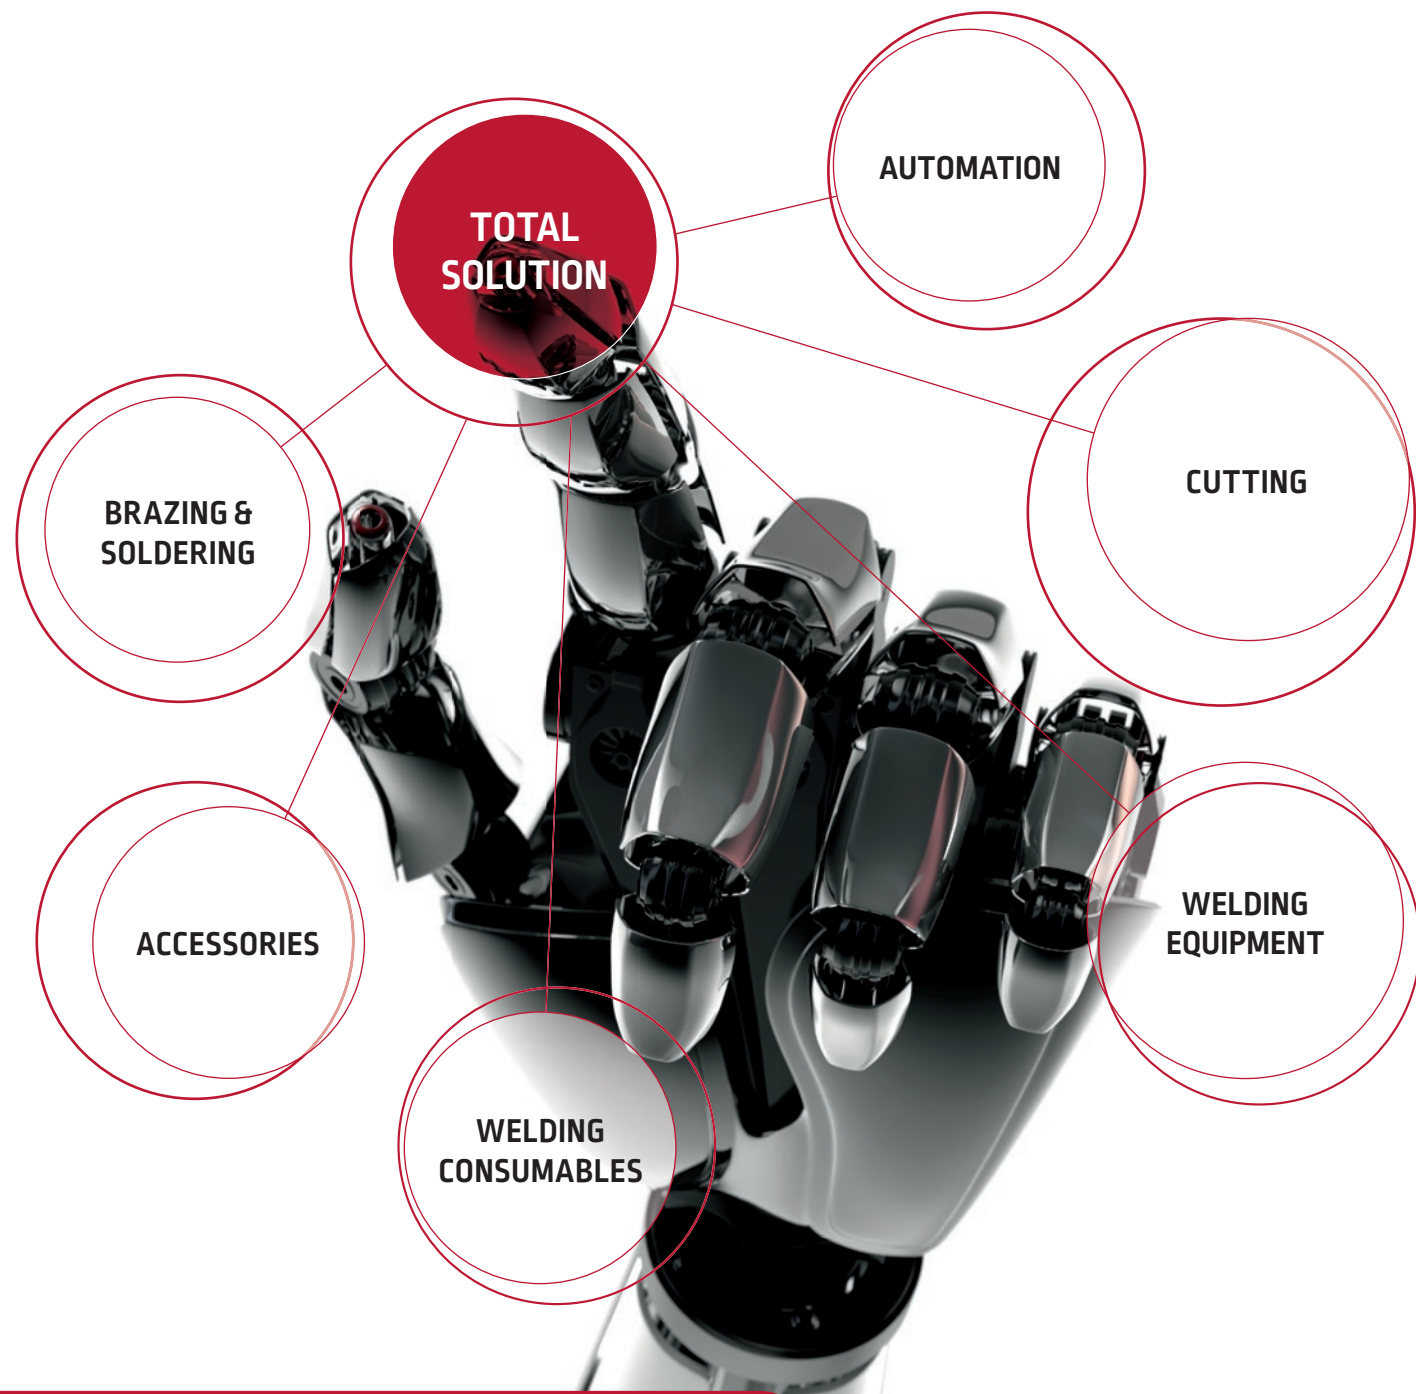

## TABLE OF CONTENTS

Corporate Information	2
LNG Introduction	5
Main Applications and Base materials	8
Storage Tank	9
Cryogenic Piping	16
Heat Exchanger	16
LNG Carrier	17
Mechanized solution	19
Consumables Table	20

**BEING PRESENT LOCALLY**  
MAKES US MORE AWARE GLOBALLY

Benefit from the Market Leader

**SPECIAL ALLOYS™**

**120**  
YEARS OF EXPERIENCE

**1**  
NUMBER ONE  
IN WELDING

**325**  
R&D ENGINEERS  
WORLDWIDE



**11 000**  
EMPLOYEES WORLDWIDE

**LOCATIONS**

- Global Headquarters
- Solution Centers

**2.7**  
BILLION USD REVENUE

**42**  
SOLUTION  
CENTERS

**160** ACTIVE IN 160  
COUNTRIES  
WORLDWIDE


# LNG

## LIQUEFIED NATURAL GAS


Natural gas mainly in the form of Methane, after being extracted from gas fields, will be processed in a gas processing plant where its impurities such as CO<sub>2</sub>, Water & Sulfur will be removed. Now it is time to transport the gas to the end users for distribution. Eventually, either a gas pipeline will be used or Natural gas gets liquefied at cryogenic temperature of -265°F (-160°C). When natural gas is turned into LNG, its volume shrinks by a factor of 600. This reduction in volume enables the gas to be transported economically over long distances.

### FIVE DIFFERENT TYPES OF LNG FACILITIES

1. LNG Export Terminal (Liquefaction)
2. LNG Import Terminal (Regasification)
3. LNG Peak-shaving
4. Floating LNG (FLNG)
5. LNG Carriers

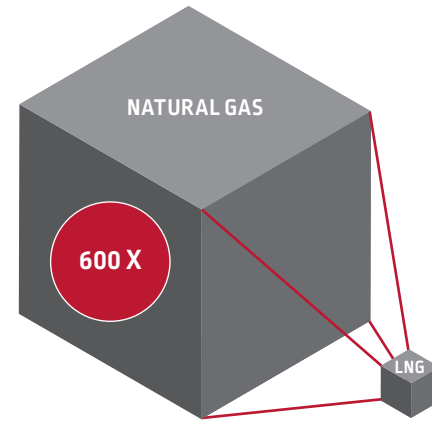

Lincoln Electric offers Total Welding Solution for all parts of the LNG value chain. Storage Tanks, Cryogenic Piping, Carriers and Heat Exchanger.

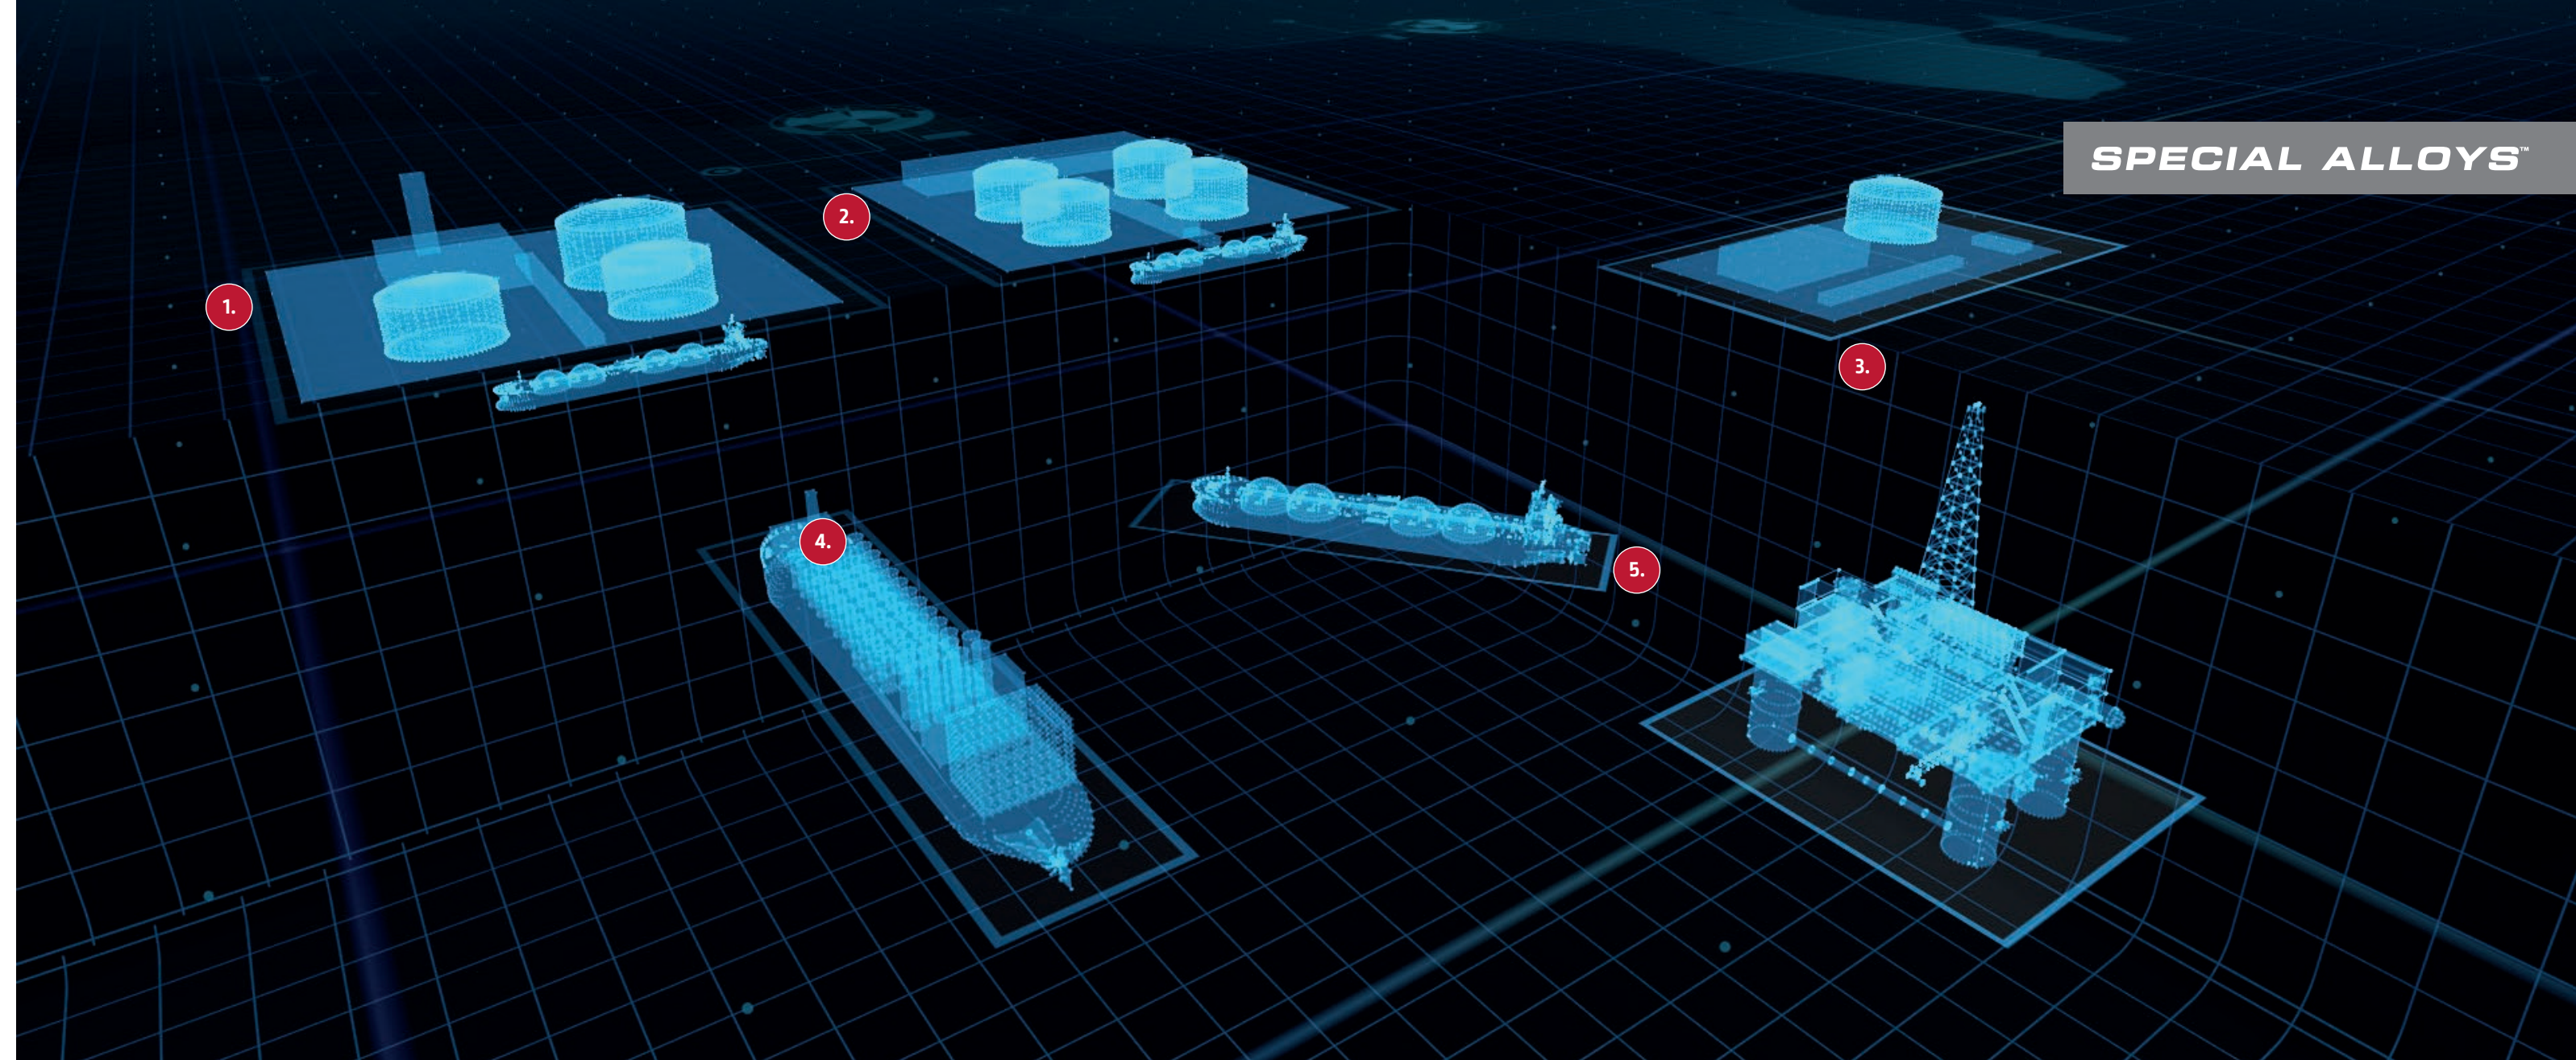

SPECIAL ALLOYS™

1.

### LNG EXPORT TERMINAL (LIQUEFACTION)

Refrigeration process is the core of an LNG plant in which natural gas is cooled and liquefied to -160°C or less using the principle of refrigeration. Because gas is cooled and liquefied to an extremely-low temperature during the process, an enormous amount of energy is consumed. How much this energy can be reduced is important, so various ingenious processes are used. Such as C3-MR, AP-X, Cascade, DMR & SMR. The refrigeration process happens in multiple steps and requires various Heat Exchanger types and Compressor systems.

2.

### LNG IMPORT TERMINAL (REGASIFICATION)

LNG will be shipped to destination port. In order to be used as Natural gas again it has to get vaporized (Re-gasified). There are various Heat Exchangers (vaporizers) used to vaporize the LNG. Depending on the vaporizer type, Seawater, Ambient Air, Propane or Burnt LNG is used to vaporize the LNG. We have specialized welding solutions for fabrication of Re-gasification plant components.

3.

### LNG PEAK-SHAVING

LNG as fuel has seasonality, in some export terminals there is a peak shaving facility to store the LNG for most of the year and export it at the most demanding season of the year.

4.

### FLOATING LNG (FLNG)

Floating LNG is a floating Offshore unit which has the capability of Liquefaction or Regasification of Natural gas right at the Offshore topside. LNG FPSO refers to LNG Floating Production Storage and Offloading Unit which does the gas processing and Liquefaction.

Floating LNG can also be Regasification units. Instead of investing in fix regasification terminals, a floating unit can travel to the end destination to re-gasify the LNG. It is called FSRU referring to Floating Storage & Regasification Unit.

5.

### LNG CARRIERS

In order to transport LNG from liquefaction or Peak shaving terminal to an end user location, LNG carriers are needed. There are also ships which sail with LNG as fuel. All such carriers require special materials, insulation and welding solutions. We offer Total welding solutions for all LNG carrier types.

# MAIN APPLICATIONS AND BASE MATERIALS

## STORAGE TANKS



- 9% Nickel
- C-Mn steel
- Al 5083
- Piping: 304L

## CRYOGENIC HEAT EXCHANGER



- Al 5083
- Al 6063
- 304L
- 316L

## CRYOGENIC PIPING



- 304L
- 316L

## LNG CARRIER



- 5% Nickel
- 9% Nickel
- Al 5083
- 304L
- FeNi36 (Invar) alloy

## LNG PROJECT

A LNG project can take more than 6 years to build from the Final Investment Decision (FID). Due to complexity of construction and high level of safety control, construction of storage tanks alone can take up to 3 years.

**Welding is a small but key element in execution of LNG projects. Quality consumables along with mechanized welding solutions minimize the risks.**

# LNG STORAGE TANKS & CONTAINMENT TYPES





**SPECIAL ALLOYS™**

LNG storage tanks are highly critical components of LNG industry. Storage tanks can be categorized from different aspects.

- Fix or on carrier tanks
- Containment Type
- Above Ground, In-Ground types & Under-Ground

**FIXED STORAGE TANKS CAN NORMALLY BE DESIGNED USING ONE OF FOUR CONTAINMENT TYPES**

- Single Containment
- Double Containment
- Full Containment
- Membrane Type

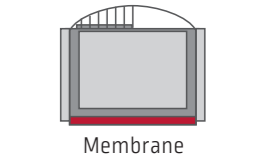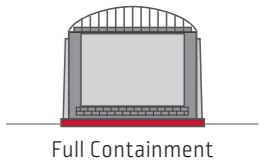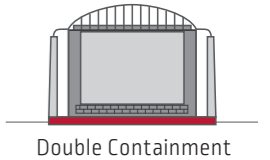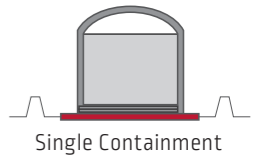

## DESIGN ASPECTS

The balance between the required land, construction, cost and local legislation defines the containment type. Various design codes govern the construction of LNG tanks.

- ASME BPVC Sec. VIII, Div. 1
- ASME BPVC Sec. VIII Div. 2
- API 620
- NFPA 59A
- API 660
- BS EN 14620-1:
- JIS B8265:
- JIS B8267

Liquefaction temperature for some types of gas and its suitable material for transport or storage

Table 1) Boiling temperature of cryogenic gases vs materials for liquid storage

Steel grade	Boiling temp. (°C)	Gas
<b>Fine grained steel</b>	-28	CO2 (to 1.5)
<b>1% Ni steel</b>	-42	Propane
<b>2.5% Ni steel</b>	-78	CO2 (solid)
	-84	Acetylene
	-88	Ethane
<b>3.5% Ni steel</b>	-104	Ethylene
<b>5% Ni steel</b>	-153	Krypton
<b>9% Ni steel</b>	-161	Methane
<b>Aluminium</b>	-183	Oxygen
	-186	Argon
	-196	Nitrogen
	-253	Hydrogen
	-269	Helium

Table 2) Typical properties of 9% Nickel steel plates

Item	ASTM	
	A353	A553 Type I
Yield strength 0.2% Proof stress (MPa)	≥515	≥585
Tensile strength (MPa)	690-825	
Elongation (%), t:Thick (mm)	≥20.0	
Charpy (J) at -196°C	≥34	
Lateral expansion*3 (mm) at -196°C	≥0.38	
Thickness (mm)	50	50
Heat treatment	Normalized/T	QT
C (%)	≤0.13	
Si (%)	0.15-0.40	
Mn (%)	≤0.90	
P (%)	≤0.035	
S (%)	≤0.035	
Ni (%)	8.50-9.50	


**9% NICKEL IS THE MAIN GRADE USED FOR FABRICATION OF LNG INNER TANKS CONSIDERING THE VERY LOW OPERATING TEMPERATURE**

# FULL CONTAINMENT LNG TANK


Full containment has become the most commonly built LNG tank type due to its safety and economical value.

The inner tank is made of 9% Nickel steel and the outer tank is made of Pre-stressed concrete (PC). Between the inner and outer tank there is a vapor barrier made of thin carbon steel plate and many different types of insulations.

The roof can be made of concrete or 9% Nickel material depending on the design. There is an Aluminium suspended deck hanging from the roof. You can view the complete LNG tank fabrication sequence in our LEAD application.



Please find more information according to our new APP on page 18

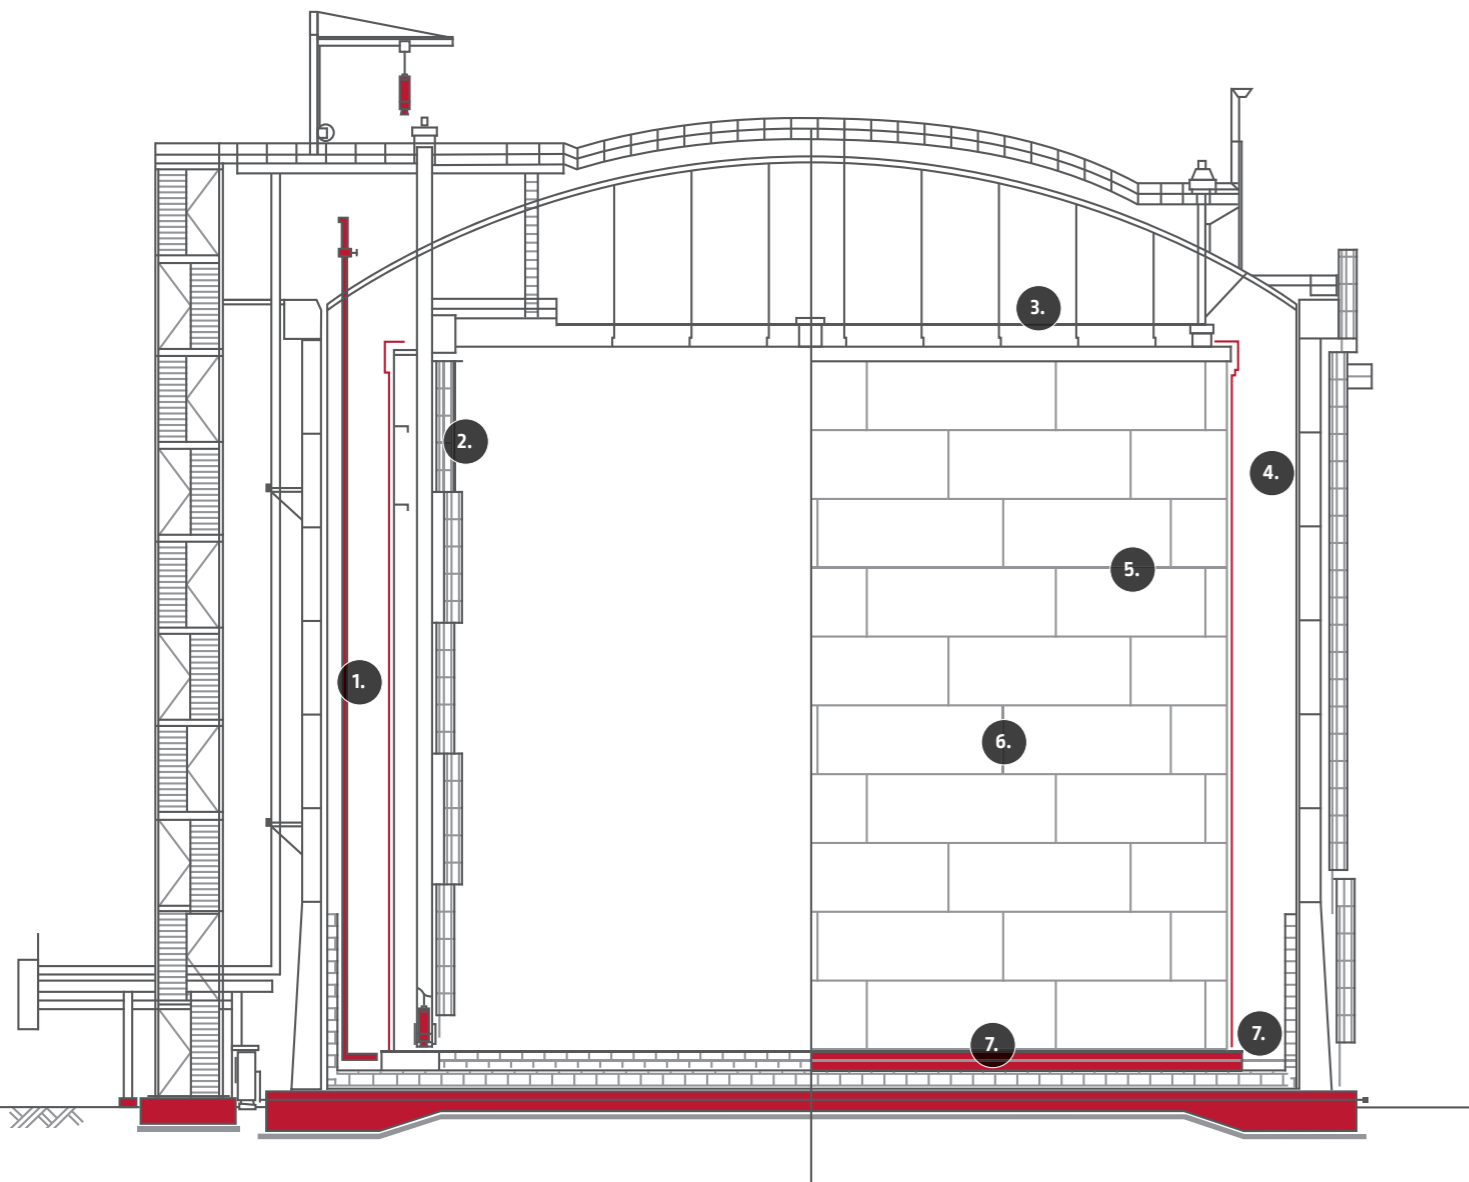

## 1. VAPOR BARRIER

It is made of carbon steel and is normally of a very low thickness. This is a protective layer between the inner tank insulation and concrete. Having a very low thickness the best method to weld this application will be cored wire to avoid unnecessary distortion.

## 2. INTERNAL PIPING

Liquefied gas is transferred to and from the tank via stainless steel piping. The piping requires special consumables to guarantee the required toughness / lateral expansion.

## 3. SUSPENDED DECK

Carbon or stainless steel rods are attached from deck stiffeners to the roof girders or rafters. The suspended decks require a deck annular plate to provide a vapor seal between the liquid product and the vapor space above the primary containment. The deck is made of Aluminium alloy 5083.

## 4. INNER TANK KNUCKLE JOINTS

Top stiffener joints require welding in 4F/4G position. To that end we have developed Nyloid 4 electrode to be able to weld in overhead position. The electrode has special slag design ensuring stable arc and providing sound weld metal.

## 5. INNER TANK HORIZONTAL JOINTS

Each two 9% Nickel plates are welded in the vertical up position. Welding can be performed simultaneously from both sides or one followed by another. Typically alloy 276 is used for this application.

## 6. INNER TANK VERTICAL JOINTS

9% Nickel vertical joints are welded in vertical up. For this reason either SMAW electrode is applied manually or FCW for semi-automatic and fully automatic welding.

## 7. INNER TANK BOTTOM

The bottom plates corners are normally welded in the 2G welding position. In most of the designs a horizontal 2G joint is used. Normally bottom plates are pre-joined in workshop using the SAW process and then will be welded together with FCAW or SMAW on the jobsite.

# SPECIAL ALLOYS™

### SMAW:

- Conarc 51
- Conarc 49C

### FCAW:

- Outershield
- MC460VD-H

### SMAW:

- Ultramet 308LCF
- Ultramet 316LCF

### FCAW:

- Supercore 308LCF
- Supercore 316LCF

### GTAW:

- ER308LCF
- ER316LCF

### SAW:

- ER308LCF + P2007
- ER316LCF + P2007

### GTAW:

- Superglaze 5183

### GMAW:

- Superglaze 5183

### SMAW:

- Nyloid 4

### SAW:

- LNS NiCroMo 60/16 + P2007
- LNS NiCro 60/20 + P2007
- Techalloy 276 + P2007
- Techalloy 625 + P2007

### SMAW:

- Nyloid 2
- NIMROD 625KS

### FCAW:

- Supercore 625P

### SMAW:

- Nyloid 2
- NIMROD 625KS

### FCAW:

- Supercore 625P

### SAW:

- LNS NiCroMo 60/16 + P2007
- LNS NiCro 60/20 + P2007

# INNER TANK HORIZONTAL JOINTS

Welding of horizontal joints in the 2G welding position is one of the most critical steps of LNG tank fabrication. Lincoln electric offers a full product portfolio of consumables and equipment as well as the automation package.

## A 200,000m<sup>3</sup> LNG TANK CAN HAVE AN INNER TANK WITH 10 SHELL COURSES.

- Joint Opening
  - > With Opening
  - > W/O Opening
- Welding Sequence
  - > Single sided
  - > Double sided
- Joint Symmetry
  - > Compound 1/2 - 1/2
  - > Compound 1/3 - 2/3

**SAW is the dominant process for welding of Horizontal joints. It offers the highest productivity. It is key to keep the balance among penetration, dilution and deposition rate.**

### THERE ARE GENERALLY TWO METHODS OF SAW WELDING OF 2G JOINTS:

- Single-sided: Whether it is a single V joint or a compound joint, welding will be finished on one side and then welding on the opposite side will be started.
- Double-sided welding: Will be performed on compound joint, which has currently become a standard joint design for thicknesses above 11mm

Figure 2) Torch positioning for 2G double sided SAW


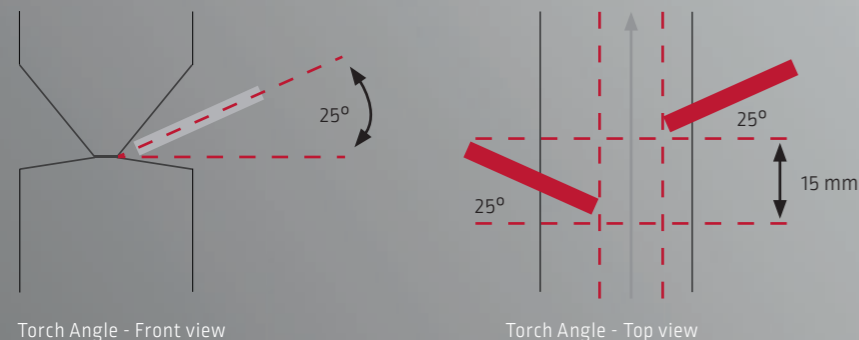


Figure 1) Various joints design for 2G SAW

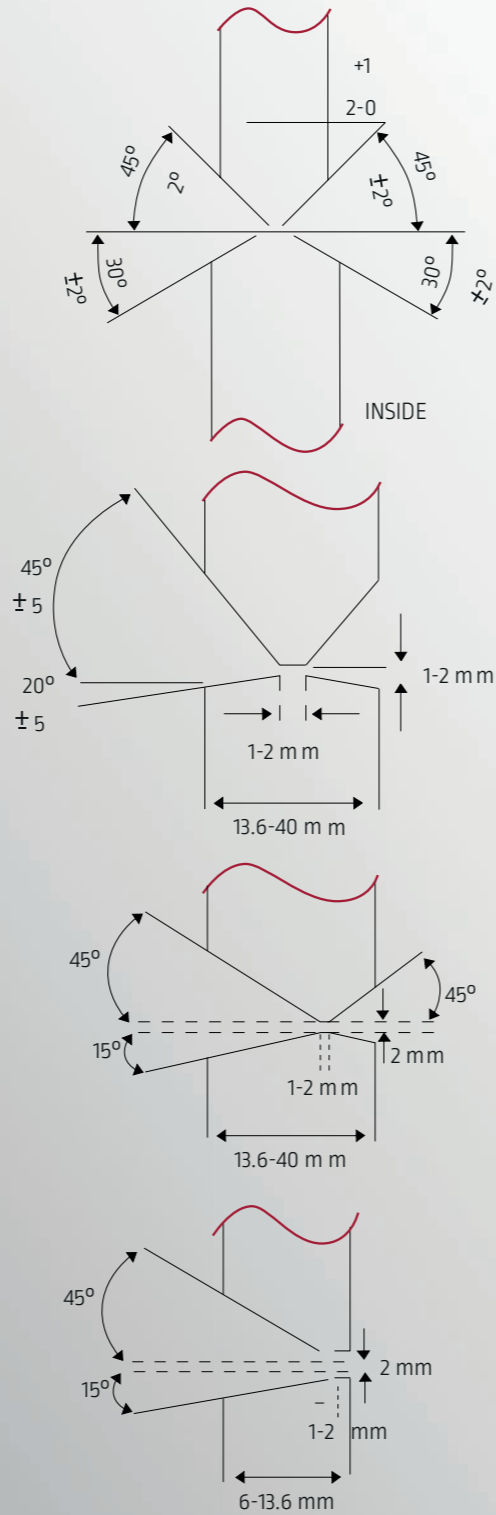

## SPECIAL ALLOYS™

Alloys 276 has been the dominant alloy due to its higher resistance to hot cracking and subsequently larger diameter welding.

Alloy Type	SA Wire	Flux
Ni 625	LNS NiCroMo 60/20 (TECHMERGE S NI625)	P2007 (TECHMERGE F P2007)
Ni 276	LNS NiCroMo 60/16 (TECHMERGE S NI276)	P2007 (TECHMERGE F P2007)

With the help of PowerWave® and Waveform Control Technology we can achieve a balance among penetration, mechanical properties, heat input and productivity.

We have conducted numerous trials and been able to design a special Waveform for Nickel base alloys applied for double sided SAW horizontal welding.

Table 3) Effect of AC/DC balance on welding parameters and heat input of double sided 2G welding

Arc	Pass	Voltage	Current	WFS (IPM) [cm]	Wave Balance	DC Offset	Frequency	Phase Angle	Travel Speed (IPM) [cm/min]	Deposition Lb/Hr [Kg/Hr]	Head Input kJ/in [kJ/mm]
Side 1	Root	26	290-310	100 [254]	60	0	80		13 [33]	12.6 [5.7]	36 [1.4]
Side 2	Root	27	290-310	100 [254]	60	15	80	180	13 [33]	12.6 [5.7]	37.4 [1.5]
Side 1	2	29	300-320	105 [267]	60	10	80		20 [51]	13.25 [6]	26.8 [1.05]
Side 2	2	29	300-320	105 [267]	60	10	80	180	20 [51]	13.25 [6]	26.8 [1.05]
Side 1	3	29	300-320	105 [267]	60	10	80		20 [51]	13.25 [6]	26.8 [1.05]
Side 2	3	29	300-320	105 [267]	60	10	80	180	20 [51]	13.25 [6]	26.8 [1.05]
Side 1	4	29	300-320	105 [267]	60	10	80		24 [61]	13.25 [6]	23.5 [925]
Side 2	4	29	300-320	105 [267]	60	10	80	180	24 [61]	13.25 [6]	23.5 [925]
Side 1	5	29	300-320	105 [267]	60	10	80		24 [61]	13.25 [6]	23.5 [925]
Side 2	5	29	300-320	105 [267]	60	10	80	180	24 [61]	13.25 [6]	23.5 [925]
Side 1	6	29	300-320	105 [267]	60	10	80		24 [61]	13.25 [6]	23.5 [925]
Side 2	6	29	300-320	105 [267]	60	10	80	180	24 [61]	13.25 [6]	23.5 [925]

# INNER TANK VERTICAL JOINTS

**FOR VERTICAL JOINTS SMAW AND FCAW ARE THE DOMINANT PROCESSES.**

For manual process Nyloid 2 has been used for decades in many projects worldwide as the electrode of choice and Supercore 625P FCW is proven to offer the best combination of excellent weldability and mechanical properties.

**Nyloid 2 has been applied for decades in numerous LNG projects. Its extra high metal recovery revolutionized the manual welding of the vertical joint.**

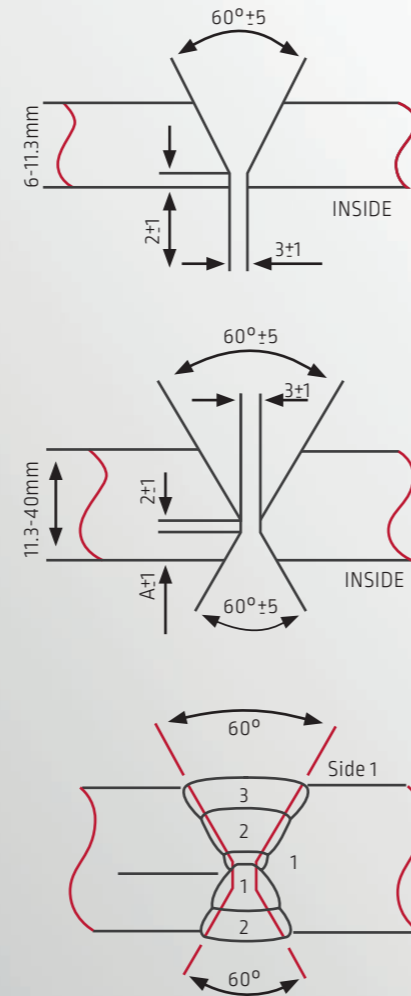


Table 4) All weld metal mechanical properties of Supercore 625P (weld type: as per AWS A5.34; shielding gas: M21; Test condition: As-welded)

Welding position	Tensile properties					Impact toughness -196°C		Fracture toughness -170°C
	Rp0.2, MPa	Rm, MPa	A4, %	A5, %	Z, %	CVN, J	LE, mm	CTOD, mm
PA-1G	500	770	44	43	41	70	1.20	-
PF-3G	500	760	46	43	42	86	1.44	0.50

Table 5) 9%Ni steel joint procedure test data of Supercore 625P (shielding gas: M21; Test condition: As-welded)

Welding position	Method	Thickness mm	Joint type <sup>(1)</sup>	Cross-weld tensile MPa	Bend test			Charpy impact test -196°C		
					T-V <sup>(2)</sup>	L-face <sup>(3)</sup>	L-root <sup>(3)</sup>	Location	CVN, J	LE, mm
PF-3G	Semi-Auto	13	60° D-V [2/3, 1/3]	750	pass	pass	pass	Mid-T	89	1.22
PF-3G	Semi-Auto	20	60° D-V [1/2, 1/2]	739	pass	pass	pass	Mid-T	75	1.05
PF-3G	Full mech.	25	60° D-V [2/3, 1/3]	715	pass	pass	pass	Mid-T	86 72	1.6 0.9
PF-3G	Semi-Auto	13	45°±15° [2/3, 1/3]	742	pass	pass	pass	Mid-T	91	0.79

Note: [1] D-V=double V; [2] T=transverse; [3] L=Longitudinal

**SPECIAL ALLOYS™**

**Supercore 625P is now the reference FCW that combines excellent weldability and mechanical properties.**

Process	Classification	Product Name
<b>SMAW</b>	A5.11: ENiCrMo-3	<b>NIMROD 625KS</b> (TECHRODE Ni625KS)
<b>SMAW</b>	A5.11: ENiCrMo-6	<b>Nyloid 2</b> (TECHRODE Ni620)
<b>FCAW</b>	A5.34: ENiCrMo3T1-4	<b>Supercore 625P</b> (TECHCORE Ni625P)

In cooperation with AllTime Welding

www.lincolnelectric.eu

WELDING SOLUTIONS FOR THE LNG INDUSTRY

## CRYOGENIC PIPING STAINLESS STEEL

### FERRITE CONTROL

Base materials are carefully processed. Weld metals are as-cast and do not necessarily achieve the required toughness.


### HOW TO ACHIEVE WELD METAL IMPACT PROPERTIES?

- Solution annealing
- Fully austenitic consumables
- Gas shielded processes
- Specially designed **Controlled Ferrite** consumables


### VARIOUS STANDARDS HAVE FERRITE LIMITS FOR STAINLESS STEELS, FOR EXAMPLE:

ASME III requires 5FN minimum; 3-10FN for service above 427°C. API 582 has 3FN minimum, it is noted that for cryogenic service lower FN may be required.

**It is proven that a narrow controlled Ferrite between 2-5FN guarantees the required mechanical properties under cryogenic conditions. Our LCF consumables have been welded in LNG projects for the last 3 decades.**

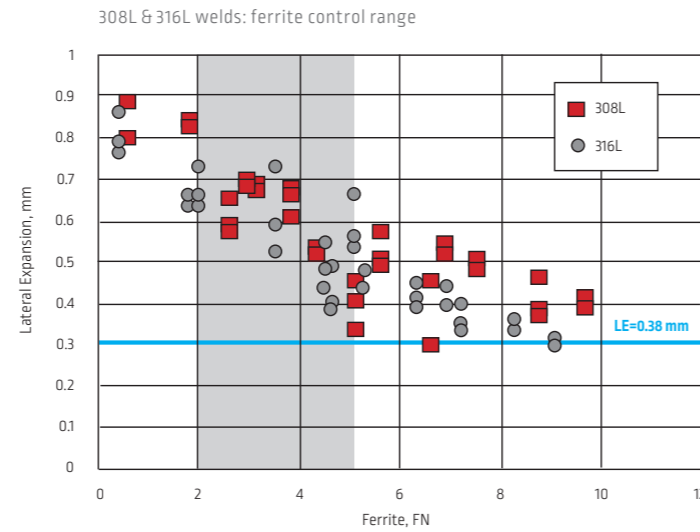

Figures 3) Effect of FN on lateral expansion for Austenitic grades

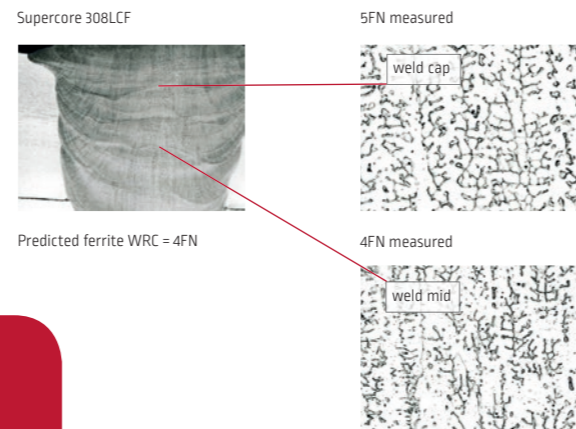

## HEAT EXCHANGER

Various heat exchanger are used in LNG facilities

Heat exchangers in LNG industry play a huge role. The entire refrigeration or re-gasification process relies on multi step exchange of heat.

C-Mn and stainless steel or Aluminium alloys are applied. Aluminum alloys of 6XXX and 5XXX are most commonly used grades. Our Superglaze products have a long presence in LNG applications

### LIQUEFACTION:

- Main Cryogenic Heat Exchanger (MCHE)
- Spiral Wound Heat Exchanger (SWHE)
- Plate-Fin Heat Exchanger (PFHE)

### REGASIFICATION:

- Vaporizers
- Boil-off gas Re-condenser

## LNG CARRIERS

### LNG CARRIER HAVE DIFFERENT STORAGE TANK DESIGNS:


- Integral (Dependent)
- Independent

Integral tanks are built inside the carrier hull. The base material is carbon steel covered by insulation and on top of the insulation there is membrane cladding with stainless steel or Invar (36% Nickel) straps.

### INDEPENDENT TANKS ARE

- Type ,A' (fully refrigerated)
- Type ,B' (typical LNG tank)
- Type ,C' (fully pressurized)

Depending on the design of the independent tank different materials such as Aluminium Alloy, Austenitic stainless, 5% & 9% Nickel material is utilized

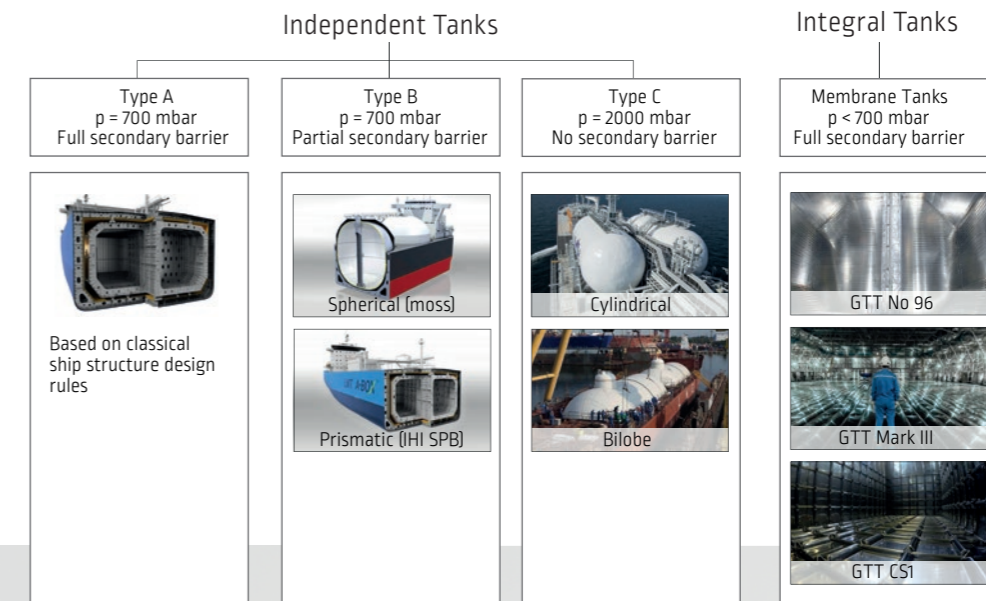

## ALUMINIUM WELDING

Let us put our experience to work for you

### FULLY INTEGRATED ALUMINIUM MIG WIRE FACILITY

As a major supplier of welding wire, Lincoln Electric is the leader in GMAW wire manufacturing technology. We carry that same technology and expertise to our Aluminium GMAW wire manufacturing. Lincoln Electric has the only fully integrated Aluminum GMAW wire facility in the world. We start from raw primary aluminum




and then use state-of-the-art equipment to produce a complete range of aluminum alloys including 1100, 1070, 2319, 4043, 4047, 5087, 5183, 5356, 5554 and 5556. This gives us full control of welding chemistry throughout the process as well as the ability to always deliver product to our customer, regardless of market conditions.





**DOWNLOAD  
LEAD (APP)**

Download our **Lincoln Electric Application Data center (LEAD for short)** and find out more information about numerous Industry applications and consumables

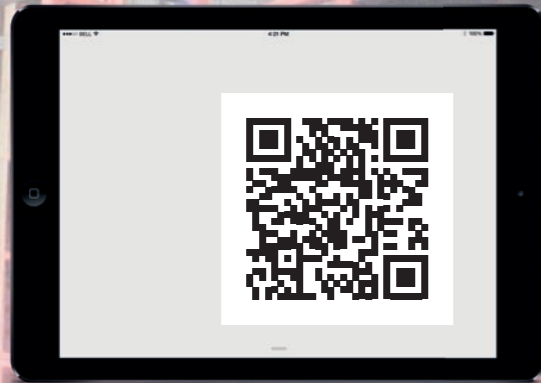

**VERTICAL  
JOINTS**

**HORIZONTAL  
JOINTS**

**MECHANIZED  
SOLUTIONS**

**GRINDING**

**PROCESS  
PIPING**

**CONSUMABLES**


**PLASMA  
GOUGING**

**INTEGRATION &  
TRAINING**

**TOTAL SOLUTION  
FOR LNG TANK  
AND PIPING  
FABRICATION**

We can offer all components for manual and mechanized welding of LNG components.

**SPECIAL ALLOYS™**

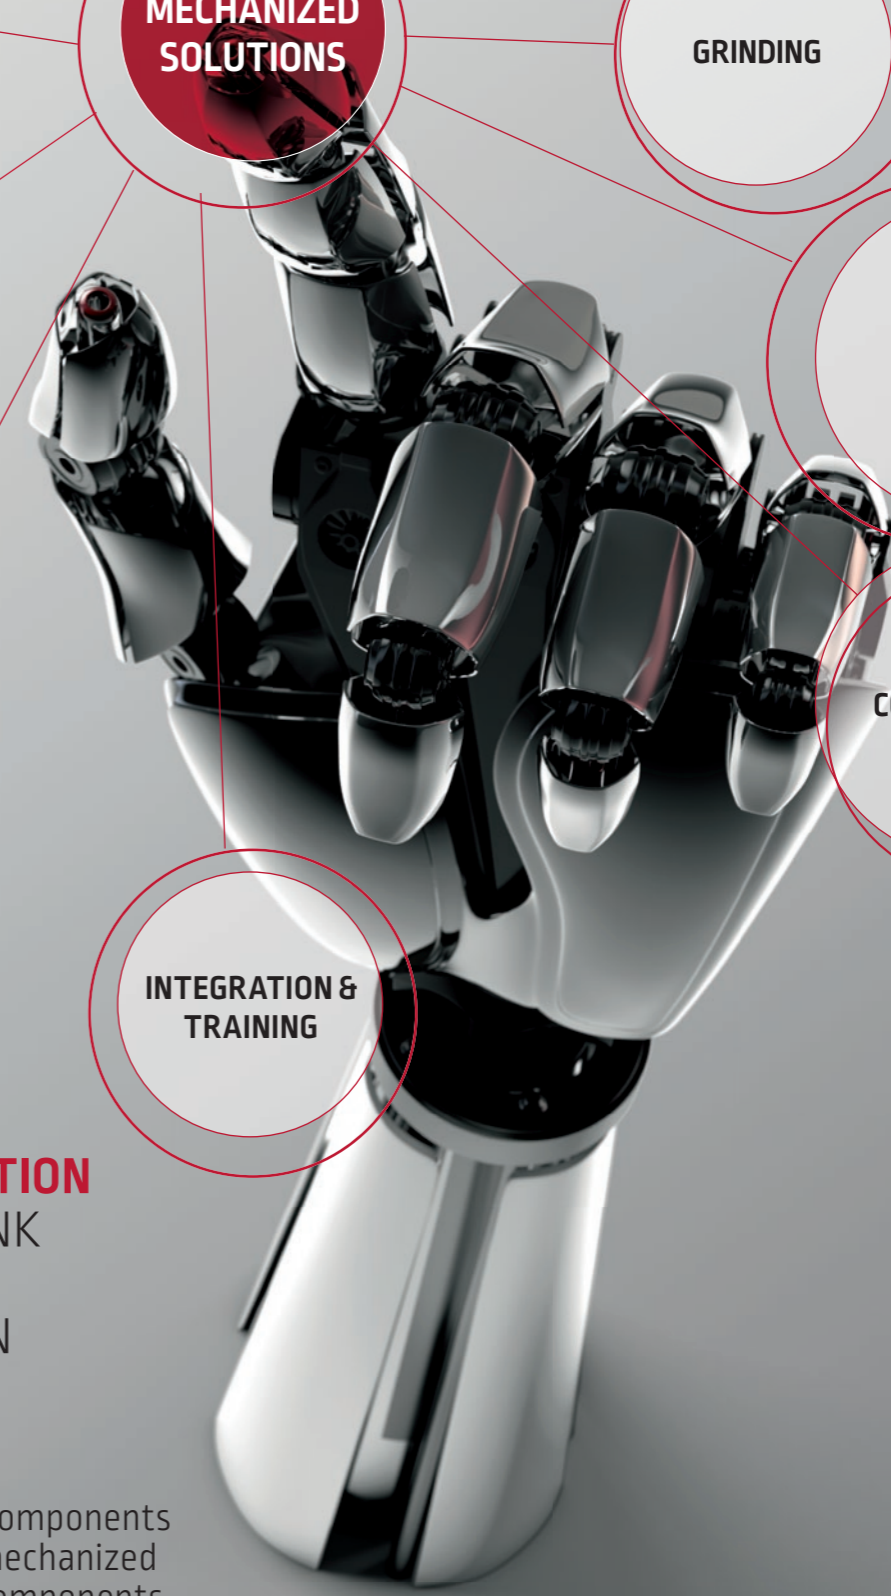

In cooperation with AllTime Welding

**UNALLOYED STEELS // MILD STEEL CONSUMABLES**

Alloy Type	Welding Process	Product Name and Specification		
		Product Name	AWS	BS / EN / ISO
C-Mn	SMAW	CONARC 49C	A5.1: E7018-1-H4R	BS EN ISO 2560-A: E 46 4 B 32 H5
		CONARC 51	A5.1: E7016-1-H4R	BS EN ISO 2560-A: E 42 4 B 12 H5
	GMAW	SUPRAMIG ULTRA	A5.18: ER70S-6	BS EN ISO 14341-A: G50 5 M21 4Si1/G46 3 C1 4Si1
	GTAW	LNT 25	A5.18: ER70S-3	BS EN ISO 636: W 42 5 W2Si
		LNT 26	A5.18: ER70S-6	BS EN ISO 636: W 42 5 W3Si1
	MCAW	OUTERSHIELD MC460VD-H	A5.18: E70C-6M H4	BS EN ISO 17632-A: T 46 2 M M 1 H5
	SAW (780)	L-61	A5.17: EM12K	BS EN ISO 14171-A: S2Si
	SAW (P230)	L-50M	A5.17: EH12K	BS EN ISO 14171-A: S3Si

**STAINLESS STEEL // CRYOGENIC STAINLESS STEEL CONSUMABLES**

Alloy Type	Welding Process	Product Name and Specification		
		Product Name	AWS	BS / EN / ISO
Cryogenic 308L	SMAW	ULTRAMET 308LCF (TECHTRODE 308LCF)	A5.4: E308L-16	BS EN ISO 3581-A: E 19 9 L R 3 2
		ULTRAMET B308LCF (TECHTRODE 308LBFCF)	A5.4: E308L-15	BS EN ISO 3581-A: E 19 9 L B 4 2
	GTAW	ER308LCF (TECHTIG 308LCF)	A5.9: ER308L	BS EN ISO 14343-A: W 19 9 L
	FCAW	SUPERCORE308LCF (TECHCORE 308LCF)	A5.22: ER308LT1-1/4J	BS EN ISO 17633-A: T 19 9 L P C/M 2
SAW (P2007)	ER308LCF (TECHMERGE S 308LCF)	A5.9: ER308L	BS EN ISO 14343-A: S 19 9 L	
Cryogenic 316L	SMAW	ULTRAMET 316LCF (TECHTRODE 316LCF)	A5.9: ER308L	-
		ULTRAMET B316LCF (TECHTRODE 316LBFCF)	A5.4: E316L-15	-
	GTAW	ER316LCF (TECHTIG 316LCF)	A5.9: ER316L	BS EN ISO 14343-A: W 19 12 3 L
	FCAW	SUPERCORE316LCF (TECHCORE 316LCF)	A5.22: ER316LT1-1/4J	BS EN ISO 17633-B: TS 316 L FM1
	SAW (P2007)	ER316LCF (TECHMERGE S 316LCF)	A5.9: ER316L	BS EN ISO 14343-A: S 19 12 3 L

**NICKEL BASE ALLOYS // ALLOY C & B CONSUMABLES**

Alloy Type	Welding Process	Product Name and Specification		
		Product Name	AWS	BS / EN / ISO
59	SMAW	NIMROD 59KS (TECHTRODE NI59KS)	A5.11: ENiCrMo-13	BS EN ISO 14172: E Ni 6059
	GMAW	HAS 59 (TECHFIL NI59)	A5.14: ERNiCrMo-13	BS EN ISO 18274: S Ni 6059
	GTAW	HAS 59 (TECHTIG NI59)	A5.14: ERNiCrMo-13	BS EN ISO 18274: S Ni 6059
C276	SMAW	NIMROD C276KS (TECHTRODE NI276KS)	A5.11: ENiCrMo-4	BS EN ISO 14172: E Ni 6276
		TECH-ROD 276	A5.11: ENiCrMo-4	-
	GMAW	HAS C276 (TECHFIL NI276)	A5.14: ERNiCrMo-4	BS EN ISO 18274: S Ni 6276
		TECHALLOY 276	A5.14: ERNiCrMo-4	-
	GTAW	HAS C276 (TECHTIG NI276)	A5.14: ERNiCrMo-4	BS EN ISO 18274: S Ni 6276
		TECHALLOY 276	A5.14: ERNiCrMo-4	-
	SAW (P2007)	LNS NiCrMo 60/16 (TECHMERGE S NI276)	A5.14: ERNiCrMo-4	BS EN ISO 18274: S Ni 6276 (NiCr15Mo16Fe6W4)
SAW	TECHALLOY 276	A5.14: ERNiCrMo-4	-	

**NICKEL BASE ALLOYS // 625 ALLOY CONSUMABLES**

Alloy Type	Welding Process	Product Name and Specification		
		Product Name	AWS	BS / EN / ISO
625	SMAW	NIMROD 625KS (TECHTRODE NI625KS)	A5.11: ENiCrMo-3	BS EN ISO 14172: ENi 6625
		TECH-ROD 112	A5.11: ENiCrMo-3	
	GMAW	62-50 (TECHFIL NI625)	A5.14: ERNiCrMo-3	BS EN ISO 18274: SNI 6625
		TECHALLOY 625	A5.14: ERNiCrMo-3	
	GTAW	62-50 (TECHTIG NI625)	A5.14: ERNiCrMo-3	BS EN ISO 18274: SNI 6625
		TECHALLOY 625	A5.14: ERNiCrMo-3	
	FCAW	SUPERCORE 625P (TECHCORE NI625P)	A5.34: ENiCrMo3T1-1/4	BS EN ISO 12153: T Ni 6625 P C/M 2
	SAW (2007)	LNS NiCr60/20 (TECHMERGE S NI625)	A5.14: ERNiCrMo-3	BS EN ISO 18274: SNI 6625
	SAW (2007)	TECHALLOY 625	A5.14: ERNiCrMo-3	

**NICKEL BASE ALLOYS // SPECIALIST NICKEL BASE ALLOY CONSUMABLES**

Alloy Type	Welding Process	Product Name and Specification		
		Product Name	AWS	BS / EN / ISO
NiCrMo-6	SMAW	NYLOID 2 (TECHTRODE NI620)	A5.11: ENiCrMo-6	BS EN ISO 14172: E Ni 6620
		NYLOID 4 (TECHTRODE NI620A)	A5.11: ENiCrMo-6	BS EN ISO 14172: E Ni 6620

**ALUMINIUM ALLOYS**

Alloy Type	Welding Process	Product Name and Specification		
		Product Name	AWS	BS / EN / ISO
Al 5183	GMAW	SUPERGLAZE 5183	AWS A5.10: ER5183	-
	GTAW	SUPERGLAZE 5183	AWS A5.10: ER5183	-

**FLUX FOR SUBMERGED ARC WELDING**

Flux Type	Wire	Specification	Basicity Index	Polarity
780	L-61	BS EN ISO 14174: S A AR/AB 178 AC H5	0,7	DC/AC
P230	L-50M	BS EN ISO 14174: S A AB 1 67 AC H5	1,6	DC/AC
P2007 (TECHMERGE F P2007)	ER308LCF ER316LCF LNSNiCro 60/20 LNS NiCrMo 60/16 TECHALLOY 276	BS EN ISO 14174: S A AF 2 64 AC H5	1,6	DC +/-



#### CUSTOMER ASSISTANCE POLICY

The business of The Lincoln Electric Company® is manufacturing and selling high quality welding equipment, consumables, and cutting equipment. Our challenge is to meet the needs of our customers and to exceed their expectations. On occasion, purchasers may ask Lincoln Electric for information or advice about their use of our products. Our employees respond to inquiries to the best of their ability based on information provided to them by the customers and the knowledge they may have concerning the application. Our employees, however, are not in a position to verify the information provided or to evaluate the engineering requirements for the particular weldment. Accordingly, Lincoln Electric does not warrant or guarantee or assume any liability with respect to such information or advice. Moreover, the provision of such information or advice does not create, expand, or alter any warranty on our products. Any express or implied warranty that might arise from the information or advice, including any implied warranty of merchantability or any warranty of fitness for any customers' particular purpose is specifically disclaimed.

Lincoln Electric is a responsive manufacturer, but the selection and use of specific products sold by Lincoln Electric is solely within the control of, and remains the sole responsibility of the customer. Many variables beyond the control of Lincoln Electric affect the results obtained in applying these types of fabrication methods and service requirements.

Subject to Change – This information is accurate to the best of our knowledge at the time of printing. Please refer to [www.lincolnelectric.com](http://www.lincolnelectric.com) for any updated information.